

Cluster Beam Deposition and in situ Characterization of Carbyne-rich Carbon Films

L. Ravagnan, F. Siviero, C. Lenardi, P. Piseri, E. Barborini, P. Milani*

*INFN - Dipartimento di Fisica,
Università degli Studi di Milano,
Via Celoria 16, 20133 Milano, Italy*

C. Casari, A. Li Bassi, C.E. Bottani

INFN-Dipartimento di Ingegneria Nucleare, Politecnico di Milano, Via Ponzio 34/3, 20133 Milano, Italy

(Dated: February 1, 2008)

Nanostructured carbon films produced by supersonic cluster beam deposition have been studied by in situ Raman spectroscopy. Raman spectra show the formation of a sp^2 solid with a very large fraction of sp -coordinated carbyne species showing a long-term stability under ultra high vacuum. Distinct Raman contribution from polyyne and cumulene species have been observed. The long-term stability and the behavior of carbyne-rich films under different gas exposure have been characterized showing different evolution for different sp configurations. Our experiments confirm theoretical predictions and demonstrate the possibility of easily producing a stable carbyne-rich pure carbon solid. The stability of the sp^2 - sp network has important implications for astrophysics and for the production of novel carbon-based systems.

Linear carbon chains with sp hybridization are considered as fundamental constituents of the interstellar medium [1, 2]. They are abundant in circumstellar shells [1] and their presence can account for many features of the diffuse interstellar bands [1, 2]. The efforts to synthesise and study in laboratory these species has stimulated the discovery of C_{60} [3]. Several gas-phase studies of carbon clusters with linear or cyclic structure have suggested that they can be elemental building blocks of three-dimensional fullerenes and nanotubes [4].

Sp carbon chains can present alternating single and triple bonds (polyyne) or only double bonds (polycumulene) [5]. Theoretical calculations suggest that polycumulenes are less stable than polynes [5, 6]. Both species are characterized by an extremely high reactivity against oxygen and a strong tendency to interchain crosslinking [7], thus rendering the direct observation of a pure carbyne-assembled solid still a major challenge. Isolated carbynic species have been investigated in the gas phase in order to determine their geometry [4, 8]; their electronic and vibrational structure has been studied for non-interacting clusters embedded in matrices of cold rare gases [9].

Sp carbon chains have also been proposed as the elemental building blocks of a carbon allotrope called carbyne [7]. Carbyne story is very controversial: the first claims of direct observation of carbyne date back from the sixties [7, 10] however, up to now, no firm and unambiguous evidence of the existence of this allotrope has been provided [7]. Experimental results, mainly based on crystallographic recognition supporting the identification of crystalline carbyne, have been object of strong criticism up to a complete rejection of the carbyne concept [7, 11].

Although the occurrence of crystalline carbyne is still matter of debate, carbyne-rich or carbynoid solids have

been produced by synthetic strategies mainly based on chemical routes. These include oxidative coupling reactions, dehydrohalogenation of polymers, polycondensation reactions of halides, electrochemical reductive carbonization, condensation of end-capped chain molecules produced in the gas-phase [12, 13, 14, 15]. In these systems polyyne chains, assembled together, are preserved against crosslinking and chemical decomposition by the presence of metal-based species and molecular groups terminating and separating the chains.

A different approach to the synthesis of carbyne is the high temperatures and high-pressure treatment of carbon-based materials. Resistive heating of graphite, high-energy laser or ion irradiation of carbon have been suggested as possible methods to produce carbynoid materials [16]. However no definitive confirmation of the validity of these methods has been reported so far.

Raman spectroscopy is one of the techniques of choice for the study of carbon-based materials and for the identification of carbyne [7, 17]. The presence of a Raman band at roughly 2100 cm^{-1} , generated by the carbon triple bond is admitted to be one of the strongest arguments in favour of the presence of carbynes [7, 14]. Raman spectra of carbynoid materials are characterized by G and D bands in the $1200\text{--}1700\text{ cm}^{-1}$ range as in amorphous carbon and by the presence of the band in the 2100 cm^{-1} region [7, 14]. For carbyne-rich materials this band should have an intensity comparable or even greater than the amorphous contribution.

Raman spectra from chemically stabilized carbynoid systems are reported in literature, due to the high reactivity and fast ageing of the carbyne species, no Raman spectra are reported for pure carbon systems.

In this Letter we show that it is possible to produce nanostructured carbon films rich of carbyne species by depositing pure carbon clusters from a supersonic beam.

We have characterized these films by in situ Raman spectroscopy determining the contribution to the spectra coming from the polyynes and cumulene species. We have also studied the ageing of the film and the effect of different gas exposure.

The deposition of carbon clusters was performed by means of an UHV cluster beam apparatus (CLARA, cluster assembling roaming apparatus) described in detail in [18]. Cluster beams are generated by a pulsed microplasma cluster source (PMCS) [19]. Cluster mass distribution is monitored prior to deposition by a reflectron time-of-flight mass spectrometer. Cluster mass distribution is peaked around 600 atoms per cluster and it extends up to several thousands atoms per cluster. Cluster kinetic energy is roughly 0.3 eV/atom so that the deposition occurs in the low energy regime, in which negligible fragmentation of clusters takes place. In previous works we have demonstrated that low-energy carbon cluster deposition allow the production of nanostructured films retaining the memory of the precursor clusters [20, 21].

In order to perform both the synthesis and the analysis of the films under UHV conditions, we have connected CLARA with a small chamber equipped with a substrate holder capable of 3-axis translation and rotation around vertical axis. Nanostructured carbon films with a thickness of 200 nm were grown on a silicon substrate at room temperature. After the deposition the sample was positioned (by 90° rotation) in front of a fused quartz viewport. Raman measurements in back-scattering geometry have been performed in situ with a Jobin-Yvon T64000 spectrometer, in triple grating configuration (1800 gr/mm gratings) and with the 532 nm line of a frequency doubled Nd-Yag Coherent DPSS 532 laser. The detector was a liquid nitrogen cooled CCD camera. The instrument spectral resolution is below 3 cm⁻¹.

Cluster-assembled carbon films have been previously characterized ex situ by Raman spectroscopy [21]. The films have an amorphous structure with a main sp² hybridization character. The G and D features reveal a substantial amount of distortion of bond lengths and angles [22]. A weak peak at about 2100 cm⁻¹ was observed. Due to the high reactivity of carbyne this peak could be attributed to a residual presence of a primeval larger carbynoid population. Although a definitive attribution based solely on ex situ data cannot be considered as definitive.

Figure 1 shows the comparison between the ex situ and in situ Raman spectra of two films deposited in the same conditions. G and D bands are almost identical whereas the peak at 2100 cm⁻¹ has dramatically increased in intensity in the in situ spectrum (we will refer to it as “C” peak). This peak has a remarkably strong intensity and appears to be structured and composed of a main broad peak at about 2100 cm⁻¹ and a weaker shoulder centered around 1980 cm⁻¹, as evidenced by a two-gaussian

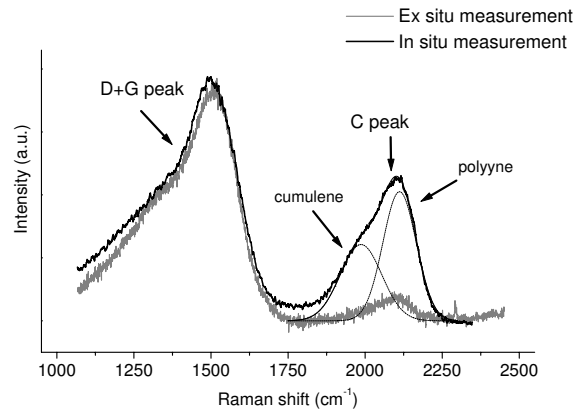


FIG. 1: Raman spectra of nanostructured carbon films deposited by a supersonic cluster beam, measured ex situ (grey) and in situ in UHV conditions (black). For the second spectra we have indicated the two fitting curves identifying the cumulene (left) and polyynes (right) contributions.

fit (see Fig. 1). The relative C peak intensity, expressed by the ratio between its integrated intensity and the D-G band integrated intensity ($I_{C\ rel} = I_C/I_{D,G}$) is roughly 45%.

Raman spectra confirm the formation, of a carbynoid material with a substantial presence of sp linear structures among a sp² hybridized disordered network, although it is not possible to quantify the amount of sp hybridized C atoms, since the Raman cross section of this kind of vibrations is unknown. Compared to other carbynoid systems reported in literature [7], the C peak at 2100 cm⁻¹ presents a low-frequency shoulder at 1980 cm⁻¹. This is caused by the presence of both cumulenic and polyyne chains coexisting in the film and giving spectral contributions at different frequencies [23]. The broadening of the two components can be ascribed to the sp chain length distribution and to disorder [7].

These observations show that a carbyne-rich material can be formed by assembling carbon clusters at very low energies without high temperature and high pressure or chemical reactions inducing carbyne formation from polymers or hydrocarbons.

We have studied the carbynoid material stability through the evolution of the C peak intensity, keeping the sample in UHV for several days (at a pressure of about $2 \cdot 10^{-9}$ Torr) and collecting Raman spectra at fixed time intervals (Fig. 2). We observed a slow decrease of the intensity of both the two components of the C peak. Again no evident changes in the shape of G and D bands has been observed. This allows us to study the C peak intensity evolution by means of the previously defined integrated intensity ratio $I_{C\ rel}$. It is also reasonable to assume a relationship between the intensity of the carbyne peaks and their concentration, even though it is not possible to make a quantitative evaluation.

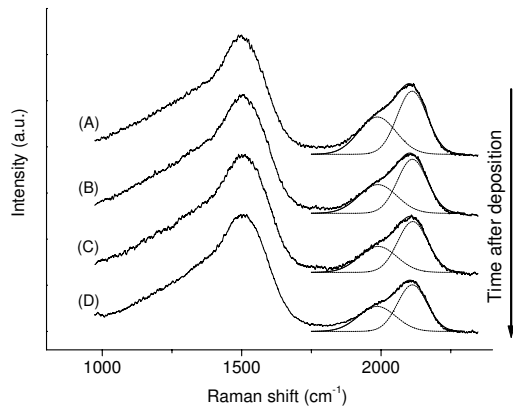


FIG. 2: Raman spectra of a 200 nm thick sample kept in UHV at different time; immediately after the deposition (A) and after 18 hours (B), 46 hours (C) and 18 days (D). Gaussian fit of the two components of the carbyne peak is also reported.

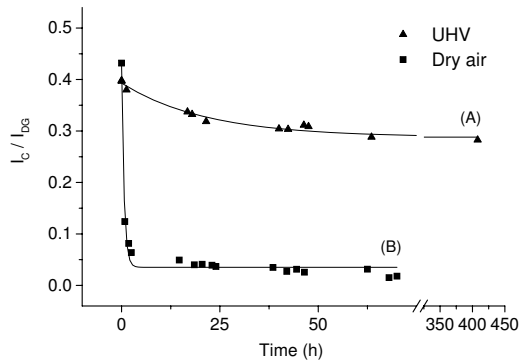


FIG. 3: Decay behaviour of the relative C peak intensity as a function of UHV residence (A) and dry air exposure time (B). The exponential plus constant fit of the experimental data is represented by the continuous line.

The temporal evolution of $I_{C \text{ rel}}$ is well described by an exponential decay plus a constant (Fig. 3). This provides an estimate of the characteristic decay time constant and of the residual non-reacted fraction of carbynes. The sample kept in UHV showed a characteristic decay time of the order of 22 hours, resulting in a reduction of $I_{C \text{ rel}}$ to a 29% of the as-deposited value. It is worth noting that this residual intensity is almost one order of magnitude greater than the intensity measured in ex situ samples, and that it remains stable even after 18 days from the deposition. In addition, the relative stability of D and G bands reveals that the amorphous structure is not significantly affected by the changes and rearrangements occurring to the carbynoid component.

This observation addresses a very important and unexpected point concerning carbyne stability: in our cluster-assembled films polyynes and cumulene species survive the

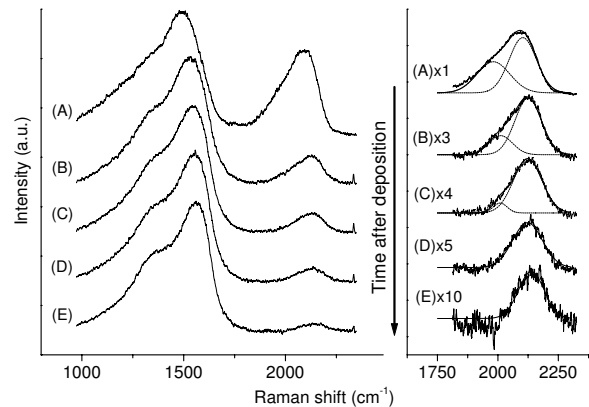


FIG. 4: Left panel: Raman spectra of a 200 nm thick sample exposed to dry air at different time; immediately after the deposition (A) and after 50 minutes (B), 110 minutes (C), 2.5 hours (D), 15 hours (E) and 70 hours (F). Right panel: evolution of the corresponding carbyne peak and gaussian fit of its two components. The scale factor is also reported.

soft landing and are stabilized in a pure carbon environment. The carbyne interaction with other types of clusters is such that after a spontaneous degradation, probably due to crosslinking, the amount of carbynoid species remains quantitatively very high and constant.

The introduction of dry air into the deposition chamber strongly modifies the Raman spectrum as shown in Fig. 4. As in the UHV experiment we have collected several Raman spectra as a function of exposure time of the film to the gas. We observed a fast decrease of the C peak intensity, (see Fig. 3) with a decay time constant of 35 minutes and a residual intensity of 3.6%, comparable with what observed in ex situ measurements [21]. The two components of the C peak behave differently under dry air exposure. After several decay times a two gaussian fit shows the complete disappearance of the lower frequency peak generated by the cumulene fraction. This indicates a more pronounced stability of the polyyne configuration against oxygen exposure, confirming the theoretical predictions [7, 23]. At the same time we have observed a 20 cm^{-1} blue shift of the position of the two peaks. According to Akagi et al. [24], the frequency of carbynic Raman peaks has an inverse dependence on the number of carbon atoms composing the chain. This behaviour suggests the attribution of the observed blue shift to a decrease in the average chain length of the deposited carbynes. Remarkably there was no clear evidence for a similar shift in UHV experiments.

In order to further clarify the role of oxygen, we have repeated the measurements exposing a film to 500 mbar of pure nitrogen (N_2). We have observed an intermediate behavior for both the decay time and the residual intensity in comparison with the UHV and dry air behavior. A blue shift of about 10 cm^{-1} was also observed, but no

disappearance of the cumulene peak took place.

The experimental results reported here provide new elements for the interpretation of the carbyne puzzle and are of relevance for areas where carbon clusters play an important role such as the composition of the interstellar medium and the existence of new allotropic forms of carbon. Low energy cluster beam deposition in an oxygen free environment appears to be a viable technique for the production of a pure carbon nanostructured material extremely rich of carbynoid species. The unexpected high stability of polyyne and cumulene species interacting with each other and with fullerene-like type of clusters once deposited [20], suggest the existence of cluster-cluster reaction mechanism leading to the formation of networks where the sp bondings are stabilized. These networks composed by sp² and sp linkages may be a disordered analogue of a new phase of carbon called graphyne and theoretically predicted by Baughman et al. [25]. The doping of this material with alkali metals or stabilising molecular groups may lead to observation of novel structural and functional properties in these systems.

The gas-phase chemical models of interstellar clouds take into account the presence of different carbon nanoparticles such as carbyne, fullerenes, polycyclic aromatic hydrocarbons etc. [1, 26]. These species are related by very complex reaction pathways to produce and destroy one species from the others. Our observations suggest that cluster-cluster interaction can produce large carbonaceous grains where carbyne species are present and stable.

In conclusion, we have characterized by in situ Raman spectroscopy nanostructured carbon films produced by supersonic cluster beam deposition in UHV conditions. Raman spectra show the presence of a large quantity of polyyne and polycumulene moieties in the films, giving origin to peaks at 2100 cm⁻¹ and 1980 cm⁻¹ respectively. The carbyne species are substantially stable in an oxygen free environment. We have characterized carbyne reactivity as a function of time in UHV and in the presence of dry air and nitrogen showing that oxygen almost completely destroys the carbyne fraction of the films. We have demonstrated that polycumulenes are less stable against oxygen compared to polyynes. The decay kinetics of the carbynoids exposed to gas gives information about the chemical and thermodynamical nature of the degradation processes. We have shown that sp car-

bon clusters can be assembled and stabilized at room temperature in a pure carbon environment allowing the spectroscopic characterization of different type of bondings. Moreover we have demonstrated the usefulness of in situ Raman spectroscopy for the study of nanostructured carbon. Our experiments open new perspectives for the production and the study of the long-sought sp carbon allotropes.

* Electronic address: pmilani@mi.infn.it

- [1] W.W. Duley, *Astrophys. J.* **528**, 841 (2000)
- [2] H.W. Kroto, J.R. Heath, S.C. O'Brien, R.F. Curl, R.E. Smalley, *Astrophys. J.* **314**, 352 (1987)
- [3] H.W. Kroto, J.R. Heath, S.C. O'Brien, R.F. Curl, R.E. Smalley, *Nature* **318**, 162 (1985)
- [4] J. Hunter, J. Fye, M.F. Jarrold, *Science* **260**, 784 (1993)
- [5] R.B. Heimann, J. Kleiman, N.M. Salansky, *Nature* **306**, 164 (1983)
- [6] M.J. Rice, S.R. Phillpot, A.R. Bishop, D.K. Campbell, *Phys. Rev. B* **34**, 4139 (1986)
- [7] for a review see: R.B. Heimann, S.E. Evsyukov, L. Kavan (eds.), *Carbyne and Carbynoid Structures*, Kluwer Academic Press, Dordrecht (1999)
- [8] M.T. Bowers, et al., *Science* **260**, 1446 (1993)
- [9] J.P. Maier, *J. Phys. Chem. A* **102**, 3462 (1998) ; J. Szczepanski et al., *Spectrochim. Acta A* **57**, 775 (2001)
- [10] A.E. Goresy, G.T. Donnay, *Science* **161**, 363 (1968)
- [11] A.G. Whittaker, *Science* **229**, 485 (1985); P.P.K. Smith, P.R. Buseck, *ibid.* **229**, 487 (1985)
- [12] Yu. P. Kudryavtsev, R.B. Heimann, S.E. Evsyukov, *J. Mater. Sci.* **31**, 5557 (1996)
- [13] L. Kavan, *Chem. Rev.* **97**, 3061 (1997)
- [14] J. Kastner et al., *Macromol.* **28**, 344 (1995); L. Kavan, et al., *Carbon* **33**, 1321 (1995)
- [15] R.J. Lagow, et al., *Science* **267**, 362 (1995)
- [16] J.A. Lenz, et al., *J. Appl. Phys.* **89**, 8284 (2001)
- [17] M. Nakamizo, R. Kammereck, P.I. Walker Jr., *Carbon* **12**, 259 (1974)
- [18] E. Barborini, et al., *Rev. Sci. Instrum.* **73**, 2060 (2002)
- [19] E. Barborini, P. Piseri, P. Milani, *J. Phys. D: Appl. Phys.* **32**, L105 (1999)
- [20] D. Donadio, et al., *Phys. Rev. Lett.* **83**, 776 (1999)
- [21] E. Barborini, et al., *Chem. Phys. Lett.* **300**, 633 (1999)
- [22] J. Robertson, *Prog. Solid State Chem.* **21**, 199 (1991)
- [23] J. Kürti, et al., *Synth. Met.* **71**, 1865 (1995)
- [24] K. Akagi, et al., *Synth. Met.* **17**, 557 (1987)
- [25] R.H. Baughman, H. Eckhardt, M. Kertesz, *J. Chem. Phys.* **87**, 6687 (1987)
- [26] R.P.A. Bettens, E. Herbst, *Astrophys. J.* **468**, 686 (1996)